Russian Academy of Sciences Joint Institute for High Temperatures RAS Institute of Problems of Chemical Physics RAS Kabardino-Balkarian State University

Physics of Extreme States of Matter — 2014

Physics of Extreme States of Matter — 2014

Edited by academician Fortov V. E., Karamurzov B. S., Efremov V. P., Khishchenko K. V., Sultanov V. G., Levashov P. R., Andreev N. E., Kanel G. I., Iosilevskiy I. L., Mintsev V. B., Petrov O. F., Savintsev A. P., Shakhray D. V., Shpatakovskaya G. V.

This compendium is devoted to investigations in the fields of thermal physics of extreme states of matter and physics of high energy densities. Different models and results of theoretical calculations of equations of state for materials at high pressures and temperatures, physics of shock, detonation and combustion waves, interaction of intense laser, x-ray and microwave radiation, powerful particle beams with matter, techniques of intense energy fluxes generation, experimental methods of diagnostics of ultrafast processes, low-temperature plasma physics, issues of physics and power engineering, as well as technology projects are considered. The majority of the works has been presented at the XXIX International Conference on Equations of State for Matter (March 1–6, 2014, Elbrus, Kabardino-Balkaria, Russia). The edition is intended for specialists in physical and technical problems of power engineering.

This conference is dedicated to the centenary of birth of academician Yakov Borisovich Zel'dovich (March 8, 1914–December 2, 1987).

The conference is sponsored by the Russian Academy of Sciences and the Russian Foundation for Basic Research (grant No. 13-02-06212).

The editorial board announces with deep regret the death of the colleagues and friends, Dr. Vladimir Vladimirovich Milyavskiy (July 22, 1969–June 12, 2013), who was the organizing and program committees member of the Conferences on Equations of State for Matter and Interaction of Intense Energy Fluxes with Matter, and Prof. Gennady Vasil'evich Sin'ko (February 7, 1950–September 8, 2013), who was a regular and active participant of these conferences starting with one of the first meeting.

CONTENTS

CHAPTER 1. EQUATIONS OF STATE FOR MATTER

Minakov D.V., Klumov B.A., Levashov P.R. Structural properties of aluminum in the vicinity of	-
melting transition	5 8 12 16
Badretdinova L.Kh., Kostitsyn O.V., Smirnov E.B., Stankevich A.V., Ten K.A., Tolochko B.P., Shakirov I.Kh. Equation of state for 1,3,5-triamino-2,4,6-trinitrobenzol based on the results of the	99
static experiments	23 28 31
accelerations and forces	33 36
Fortova S. V. Comparative analysis of the formation of vortex cascades in various problems of turbulence Khokonov A.Kh. Analytical model for the transverse vibration of graphene and (0001) graphite surface	39 42
CHAPTER 2. SHOCK WAVES. DETONATION. COMBUSTION	
$Mayer\ A.E.,\ Khishchenko\ K.V.\ Numerical\ study\ of\ shock-wave\ structure\ in\ elastic-plastic\ medium\ .$ $Anan'ev\ S.Yu.,\ Dolgoborodov\ A.Yu.,\ Mases\ M.,\ Soldatov\ A.V.,\ Lee\ J.,\ Waldbock\ J.,\ Milyavskiy\ V.V.$	45
The effect of shock wave compression on carbon nanotubes	49
ducting Cu & CuO _x interfaces	52 56
protection from space debris and micrometeorites	59
of shock-wave welding of diverse metals	61 64
different initial conditions	68 70
reaction time of nitromethane in detonation waves	72
bility limits determination	74 78
Grakhov Yu. V., Khlybov V.I. Numerical study of shock wave impacts on dynamic objects	82 87
Golovastov S. V., Korobov A.E. Influence of ejector on the efficiency of nozzle head at pulse operation Krivokorytov M.S., Golub V.V. Experimental investigation of a gas jet instabilities under acoustic	90
excitation	94 97
Bivol G. Yu., Lenkevich D.A., Golovastov S.V., Mikushkin A. Yu., Bocharnikov V.M. Parametric study of the detonation propagation in narrow channels filled with a mixture of propane butane with oxygen.	101
Drakon A.V., Emelianov A.V., Eremin A.V., Petrushevich Yu.V., Starostin A.N., Taran M.D. Experimental and theoretical study of the role of quantum effects in ignition of $\rm H_2/O_2$ and $\rm CH_4/O_2$	
mixtures doped by fire suppressants	104 108

CHAPTER 3. POWER INTERACTION WITH MATTER

Koshelev A.A., Andreev N.E. The structure of the accelerating wakefield generated by ion bunches Orlov N.Yu., Denisov O.B., Vergunova G.A., Rosmej O.N. Mathematical modeling of radiative and gas-dynamic processes in plasma for experiments, where both intense laser and heavy ion beams	
Timofeev I.S., Burdonsky I.N., Goltsov A.Yu, Makarov K.N., Leonov A.G., Yufa V.N. Spalls formation in the thin polycrystalline targets under the action of the high-power laser pulse Petrov Yu. V., Inogamov N.A. Electron-phonon scattering and related electrical conductivity in noble	119123
Migdal K.P., Petrov Yu.V., Zhakhovsky V.V., Inogamov N.A. Two-temperature equations of state for d-band metals irradiated by femtosecond laser pulses	126 129 133 135
Gurentsov E.V.; Yurischev M.V. Synthesis and characterization of Mo nanoparticles using laser based techniques	138 142
CHAPTER 4. PHYSICS OF LOW TEMPERATURE PLASMA	
Zaporozhets Yu.B., Mintsev V.B., Gryaznov V.K., Reinholz H., Röpke G., Fortov V.E. Polarized reflectivity properties of shock-compressed plasma with strong interparticle interaction	151
mosaic copper–graphite target	15° 16° 16°
Prudnikov P.I., Rykov V.A., Zherebtsov V.A., Meshakin V.I., Glotov A.I., Bazhal S.V., Romanov V.A., Andryushin I.I., Vladimirov V.I., Deputatova L.V. Dust structures created in inert gases	160
utatova L.V. The formation and properties study of extended dusty plasma structures of non-self-	168 173
Pashchina A.S., Chinnov V.F., Andriyanova Y.N., Efimov A.V. The space—time spectroscopy of the pulsed high enthalpy plasma jet	170
Mitina A.A., Polushkin E.A., Kovalchuk A.V., Semenenko A.I., Shapoval S.Yu. Application of the ECR plasma etching for preparation of the patterned wafers for analysis of the biological liquids at THz frequencies	18
A.S., Senchenko V.N. Comprehensive studies of the effectiveness of heat-shielding materials Sargsyan M.A., Isakaev E.H., Gadzhiev M.Kh., Kavyrshin D.I., Chinnov V.F. Volumary graphite sublimation by high-enthalpy plasma stream	183 187
Klementyeva I.B., Pinchuk M.E. Formation of electrical discharges under free surface of current car-	190 191
rying fluids	19.
AUTHOR INDEX	197

ELECRTON-PHONON SCATTERING AND RELATED ELECTRICAL CONDUCTIVITY IN NOBLE AND TRANSITION METALS AT HOGH ELECTRON TEMPERATURE

Petrov Yu. V., * Inogamov N. A.

ITP RAS, Chernogolovka, Russia
*uvp49@mial.ru

Electrical conductivity of noble and transition metals due to the electron-phonon collisions is calculated in two-temperature state with hot electrons and ion temperature not exceeding the melting threshold. This state arises when the femtosecond laser pulse of the moderate intensity acts onto the metal surface. Calculated electrical resistivity shows reduction with the electron temperature increase in contrast to the ordinary growth of the electrical resistivity of metals with the increase of common temperature of electrons and ions in equilibrium state. This decrease of the electrical resistivity is more significant in the case of transition metals.

Keywords: Femtosecond laser pulse, two-temperature state, noble and transition metals, electrical resistivity, electron-phonon scattering

Introduction. When ultrashort (femtosecond) laser pulse acts onto the metal surface it causes first of all the increase of the electron temperature. Large difference between electron and ion masses retards the energy transfer from electrons to ions. That is why during some time interval the surface layer of matter irradiated by the laser pulse exists in two-temperature state with the high temperature of electrons T_e and smaller temperature of ions T_i [1]. For laser pulses of moderate intensities with the surface density of energy (fluence) taken up by the metal target up to 100 mJ/cm² electron temperature in the surface layer of a target reaches several eV [2]. At the same time the equalization of electron and ion temperatures may last several picosecond, during a time interval more long than the duration of the laser pulse. Elevated electron temperature results in the significant change of the kinetic transport characteristics of a metal which are due to the electron motion. The values of kinetic coefficients at high electron temperatures may to a great extent differ from that one at usual room temperature when the equilibrium between electrons and ions takes place. Increase of the electron temperature gives rise to the change of the electron-ion coupling coefficient $\alpha(T_e)$, which is responsible for the energy exchange between electrons and ions to give the energy transferred from electrons to ions per unit time as $\alpha(T_e)(T_e - T_i)$ [3–5]. Electron-phonon coupling determines the depth of the layer of a target heated by the laser action before the sensible change of the target volume together with the another kinetic parameter—electron heat conductivity coefficient. In metals under consideration heat propagates mainly by electrons. Both electron-ion and electron-electron collisions contribute to the heat conduction. The change of the frequency of electronelectron collisions with the electron temperature increase have been calculated in [6, 7]. Now we consider electron-phonon collisions and their contribution into the transport coefficients of metals in two-temperature state at high electron temperatures and ion temperatures not exceeding the melting threshold, namely electrical conductivity.

Electron-phonon relaxation times. As a targets for the femtosecond laser irradiation we take metals with the essential excitation of d-electrons at high electron temperatures arising in metal when heating the electron subsystem by irradiation. They are noble metals having at $T_e=0$ K completely filled d-band with the top separated from the Fermi level lying within the s-p-band by the energy interval not exceeding the value 1-2 eV which is of the order of the gap in many semiconductors (as an example we consider copper (Cu)). Another situation exists in transition metals in which the Fermi level occurs inside of d-band as well as inside of sp-band (we consider iron (Fe) to present transition metals). We use the kinetic equations for sp and d-electrons in the electric field [8] taking into account collisions of all these electrons with phonons to obtain within the τ -approach relaxation times τ_s and τ_d of respectively sp and d-electrons due to the electron-phonon scattering:

$$\tau_s(\varepsilon) = \frac{m_s/m_d H_{sd} + H_{dd} + G_{ds}}{(H_{ss} + H_{sd})(H_{dd} + G_{ds}) - H_{sd} H_{ds}}$$
 (1)

$$\tau_d(\varepsilon) = \frac{m_d/m_s H_{ds} + H_{ss} + G_{sd}}{(H_{ss} + H_{sd})(H_{dd} + G_{ds}) - H_{sd} H_{ds}}$$
 (2)

Expressions (1) and (2) define relaxation times of sp and d-electrons at those values of the electron energy when transition between sp and d-bands is possible. When the electron energy is sufficient only for sp-sp scattering, relaxation time of sp - electrons is simply

$$\tau_s(\varepsilon) = 1/H_{ss} \tag{3}$$

Here

$$H_{ss} = \int w(q) \frac{q^2}{2p^2} (2N_q + 1) \frac{2\pi}{p(2\pi\hbar)^3} m_s q dq \qquad (4)$$

$$H_{sd} = \int w(q) \frac{p'}{p} \frac{p^2 + p'^2 - q^2}{2pp'} (2N_q + 1) \frac{2\pi}{p(2\pi\hbar)^3} m_d q dq$$
(5)

$$G_{sd} = \int w(q)(2N_q + 1)\frac{2\pi}{p(2\pi\hbar)^3}m_dqdq$$
 (6)

Analogously

$$H_{dd} = \int w(q) \frac{q^2}{2v'^2} (2N_q + 1) \frac{2\pi}{v'(2\pi\hbar)^3} m_d q dq \qquad (7)$$

$$H_{ds} = \int w(q) \frac{p}{p'} \frac{p^2 + p'^2 - q^2}{2pp'} (2N_q + 1) \frac{2\pi}{p'(2\pi\hbar)^3} m_s q dq$$
(8)

$$G_{ds} = \int w(q)(2N_q + 1)\frac{2\pi}{p'(2\pi\hbar)^3} m_s q dq.$$
 (9)

 m_s , m_d are respectively effective masses of sp and delectrons. We use the parabolic approach of electron dispersion curves both in sp and d-bonds having different tops and effective masses to approximate electron density of states obtained from the density functional calculations. q is phonon quasimomentum,

$$N_q = \frac{1}{exp(\hbar\omega(q)/(kT_i)) - 1}$$

is a phonon distribution function at the temperature T_i ($\omega(q)$ - phonon frequency).

$$w_q = \frac{\pi q^2}{\omega} \left(\frac{4\pi Z n e^2}{q^2 \epsilon(q)} \right)^2$$

with n being the concentration of atoms, $\epsilon(q)$ - dielectric permittivity, Z is the effective charge of ion for its interaction with the electron through the screened Coulomn potential. p stands for the electron momentum in s-band, p' is the momentum of electron of d-band. When transition between sp and d-bands occurs as a result of electron-phonon interaction, p and p' are connected by the relation

$$p^2 - \frac{m_d}{m_s} p'^2 = 2m_s(\varepsilon_1 - \varepsilon_s),$$

where ε_s and ε_1 are bottom of sp and d-bands respectively.

By integrating over q in formulas (4-9) within the corresponding interval depending on the value of electron energy ε we obtain the relaxation times τ_s of sp and τ_d of d-electrons as functions of their energy. Then substituting them into the expressions for conductivity of sp and d-electrons

$$\sigma_s = \frac{2e^2}{3} \int \left(\frac{p}{m_s}\right)^2 \frac{1}{4kT_e cosh^2(\frac{\varepsilon-\mu}{kT_-})} \tau_s(\varepsilon) \frac{4\pi p^2 dp}{(2\pi\hbar)^3},$$

$$\sigma_d = \frac{2e^2}{3} \int \left(\frac{p'}{m_d}\right)^2 \frac{1}{4kT_e cosh^2(\frac{\varepsilon-\mu}{kT_e})} \tau_d(\varepsilon) \frac{4\pi p'^2 dp'}{(2\pi\hbar)^3},$$

we can calculate electrical conductivity and resistivity due to sp and d-electrons and total resistivity connected with the electron-phonon scattering.

Resistivity of copper and iron due to the electron-phonon collisions. Fig. shows results of calculation of the resistivity of noble metal copper as the function of electron temperature for two values of the ion temperature (300K and 1200 K), not exceeding the melting temperature.

More impressive fall of resistivity with the electron temperature growth exhibits iron, one of a sufficiently large group of transition metals. The dependence of iron resistivity on the electron temperature for the

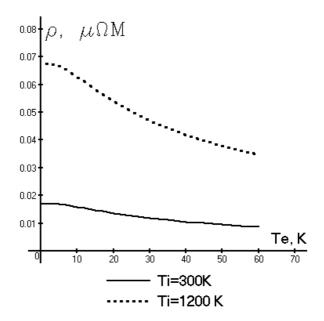


Figure 1. Electrical resistivity of copper at elevated temperature of electrons T_e for two values of the ion temperature 300K and 1200K. Resistivity drops with the electron temperature increase.

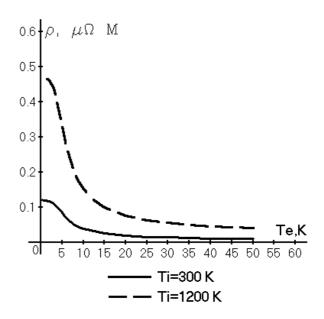


Figure 2. Resistivity of Fe in dependence on the temperature of electrons. It is obvious more significant drop of the electrical resistivity of iron than of copper in Fig. with the electron temperature increase. Ion temperature T_i takes the values 300K and 1200K.

same values of temperature of ions (300K and 1200K) is presented in Fig. 2. The fall of resistivity of metals with conducting d-electrons at high electron temperatures can be explained by the reduction of electron scattering into the d-states because of the shift of the occupancy of electron energy states into high energy states and small phonon energy.

In addition in Fig. 3 results of calculation of Cu and Fe resistivity in dependence on the common for electrons and phonon temperature in equilibrium single temperature case are shown. Resistivity of metals un-

der consideration in this case rises by the ordinary way as the temperature increases.

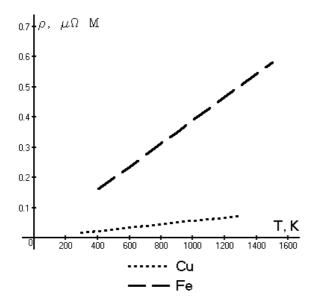


Figure 3. Calculated dependence of the resistivity of copper and iron due to the electron-phonon scattering upon the temperature of the metal in equilibrium case. Resistivity grows with the temperature increase.

Acknowledgements. This work is supported by the RFBR grant No.13-02-01078.

- Anisimov S.I., Inogamov N.A., Petrov Yu. V., Khokhlov V.A., Zhakhovskii V.V., Nishihara K., Agranat M.B., Ashitkov S.I., Komarov P.S. // Appl. Phys. A. 2008. V. 92. No 4, P. 939.
- 2. Agranat M.B., Anisimov S.I., Ashitkov S.I., Zhakhovskii V.V., Inogamov N.A., Nishihara K., Petrov Yu.V., Khokhlov V.A., Fortov V.E. // Appl. Surf. Sci. 2007. V.253. P.6276.
- Lin Z., Zhigilei L. V. // Appl. Surf. Sci. 2007. V. 253. P. 6295.
- 4. Lin Z., Zhigilei L. V., Celli V. // Phys. Rev. B. 2008. V. 77. P. 075133.
- Inogamov N. A., Petrov Yu. V., Zhakhovskii V. V., Khokhlov V. A., Demaske B. J., Ashitkov S. I., Khishchenko K. V., Migdal K. P., Agranat M. B., Anisimov S. I., Fortov V. E., Oleynik I. I. // AIP Conf. Proc. 2012. V. 1464. P. 593.
- Inogamov N. A., Petrov Yu. V. // ZhETF. 2010. V. 137. No. 3. P. 505.
- Petrov Yu. V., Inogamov N. A., Migdal K. P. // Pis'ma v ZheTF. 2013. V. 97. No. 1. P. 24.
- Mott N. F. // Proc. R. Soc. Lond. A. 1936. V. 153. P. 699.